


EBSD and BKD

Basics	TKD	Radon vs Hough	FastEBSD	Evaluation	Conclusions	Publications	Downloads	Glossary
--------	-----	----------------	----------	------------	-------------	--------------	-----------	----------

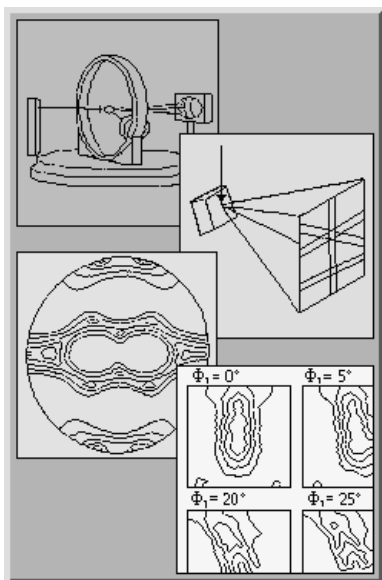

An introduction to EBSD Backscatter Kikuchi Diffraction in the Scanning Electron

Microscope



("BKD", "ACOM/SEM",
"Orientation Microscopy")

Prof. Dr. Robert Schwarzer
Kappstr. 65
D-71083 Herrenberg
Germany
E-mail: mail@ebsd.info

Revised February 21, 2026

Abstract

This web site provides a short introduction to Automated Crystal Orientation Microscopy (ACOM), a technique based on Backscatter Kikuchi Diffraction (BKD) in the Scanning Electron Microscope (SEM).

The technique is often called Electron BackScatter Diffraction (EBSD), in particular when referring to automated commercial systems. However, the acronym "EBSD" or similar abbreviations should not be mistaken for Backscatter Electron Diffraction (BED) in general. Backscatter electron diffraction from bulk surfaces comprises four well-established techniques:

- Low Energy Electron Diffraction (LEED)
- Reflection High Energy Electron Diffraction (RHEED)
- Backscatter Channeling Diffraction (ECP)
- Backscatter Kikuchi Diffraction (BKD, EBSD).

EBSD has become very popular in materials science and geology during the last decade. There are several reasons for the success of this novel technique:

- A wealth of information is obtained about the crystallography and microstructure of bulk polycrystals.
- The importance of crystal texture and materials' anisotropy has been generally realized.
- Progress in low-light level camera and computer technology has enabled fast and automated systems.
- Commercial systems are easy to operate.
- Specimen preparation is relatively simple.
- Scanning electron microscopes are widely available in many laboratories.

[Download](#)  Overview: **Backscatter and transmission Kikuchi diffraction for materials science.**

History of EBSD

1928 Shoji Nishikawa and Seishi Kikuchi

The Diffraction of Cathode Rays by Calcite.

Proc. Imperial Academy (of Japan) **4** (1928) 475-477, with 2 figures

The *first EBSD* was published by S. Kikuchi and S. Nishikawa, his supervisor, in 1928, as a compliment to Kikuchi's papers, he had published several pages before in the same volume, on similar patterns obtained in a

transmission experiment on mica foils. They directed a beam of 50 keV electrons from a gas discharge on a cleavage face of calcite at a grazing incidence of 6° . Diffraction patterns were recorded on photographic plates placed 6.4 cm behind the crystal, normal to the primary beam. The patterns consisted of pairs of parallel black and white lines, and in some cases contained diffraction spots in addition.

When the photographic plates were placed in front of the specimen (parallel with the primary beam, as nowadays in modern "EBSD" set ups), the same type of pattern was observed as well "*which must have been produced by the electrons deflected through an angle greater than 90°* ". Since transmission and backscatter patterns were quite similar, they have been likewise interpreted and indexed. The relative intensities of high-order reflections were compared with those of X-ray diffraction. Cleavage faces of mica, topaz, zincblende and a natural face of quartz were also tried, and it was found that they give similar backscatter patterns.



The authors called this new type of pattern "P-pattern" or "pattern of the fourth kind" (= "black and white lines in pairs due to multiple scattering and selective reflection"). They have later been named "transmission Kikuchi patterns" respectively "reflection Kikuchi patterns" or "backscatter Kikuchi patterns".

The low quality of the first BKP may be caused by specimen contamination due to the poor vacuum facilities at that time.



Shoji Nishikawa and Seishi Kikuchi
Diffraction of Cathode Rays by Calcite.
Nature **122** (1928) 726

A short communication in Nature appeared at the end of the same year in which Nishikawa and Kikuchi already reported the main features of BKP (bands bordered by parallel lines at a width of twice the Bragg angle; high-order reflections; center line corresponding to the section line of the lattice plane with the screen; intensity approximately predicted by the structure factor; wide-angle diffraction). In the outlook they anticipate that the above mentioned backscatter method [*today known as EBSD*] would be more useful than the transmission method on account of its possibility of extensive application on many crystals...

Seishi Kikuchi
Beugung der Materiestrahlen.
Physikalische Zeitschrift **31** (1930) 777-791

S. Kikuchi gives a review of electron and ion diffraction, at that time, by single crystals, gases and molecules. He states that the intensity profile of the (today named) Kikuchi bands is not explained by the simple kinematic theory. His focus is on the Mean Inner Potential and the Atom Form Factors for structure analysis.

In the following publications Seishi Kikuchi and Shigeo Nakagawa concentrated their studies on the deviation of the lines from the exact Bragg position caused by anomalous dispersion of crossing lines and the effect of the refractive index of the lattice on fast electrons.


S. Kikuchi and Sh. Nakagawa
On the reflection of cathode rays from single crystal surfaces. (paper in German)
Sc. Pap. Inst. Phys. Chem. Res. **21** (1933) 80-91
S. Kikuchi and Sh. Nakagawa
The anomalous reflection of fast electrons from single crystal surfaces. (paper in German)
Sc. Pap. Inst. Phys. Chem. Res. **21** (1933) 256-265

Shoji Nishikawa was Seishi Kikuchi's supervisor at the Dept. of Physics of Tokyo Imperial University.

Already in 1928, Seishi Kikuchi (August 25, 1902 - November 12, 1974) grew fond of atomic physics. He published an investigation on the mode of disintegration of Radium (J. J. Phys. **4**(1928) 143). He made the acquaintance of Werner von Heisenberg on his visit to Japan, and joined for some time Heisenberg's team at the University of Leipzig (Germany). He also visited the University of Göttingen, as a beacon of modern mathematics (David Hilbert, Richard Courant). Back in Japan in 1934, he was appointed as professor at Osaka Imperial University (now: Osaka University, Physical Science Department). He directed the construction of a 600 kV DC Cockcroft-Walton accelerator, the most powerful at that time. Seishi Kikuchi is well-known as an outstanding Japanese nuclear physicist.

1932/33 K. Shinohara
Diffraction of cathode rays by single crystals. Part III.
Sc. Pap. Inst. Phys. Chem. Res. **20** (1932/33) 39-51

Kikuchi envelopes are reported in backscatter Kikuchi patterns from cleaved calcspar (calcite, CaCO_3) at 44 keV.

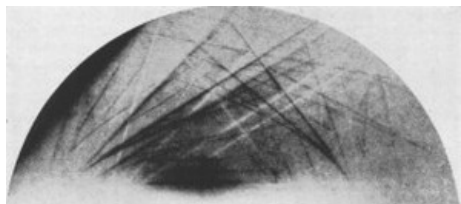

1933 R. von Meibom and E. Rupp

Wide-angle electron diffraction. (*paper in German*)

Zeitschrift für Physik **82** (1933) 690-696

In backscatter diffraction of fast electrons from rocksalt, sylvine, fluorspar, diamond, calcspar and quartz crystals, dark bands (on the photographic negative) have been reported that are bordered on both sides by (Kikuchi) lines. The bands were visible through acceptance angles up to 160° . The angle of beam incidence was varied between 3° and 30° , the beam voltage from 10 kV to 40 kV. The band width is proportional to $1/d$ (d = lattice spacing). Intensity profiles across two typical bands are sketched. Experiment showed that the bands are formed by backscattered electrons of virtually the same energy as the primary beam energy. The center lines of the bands - now called Kikuchi bands - have been indexed as zone circles sectioning the cylindrical recording film.


1937 H. Boersch

About bands in electron diffraction. (*paper in German*)

Physikalische Zeitschrift **38** (1937) 1000-1004 and image table XI

The identical publication also appeared in: Zeitschr. f. techn. Physik **18** (1937) 574-578 and image table XVI

Boersch studied thoroughly - in addition to transmission - also backscatter Kikuchi patterns (at 20 kV, about 5° of incidence and up to 162° of acceptance angle) obtained from cleaved, polished respectively etched NaCl, KCl, PbS, CaCO_3 , CaF_2 , quartz, mica, diamond, Cu and Fe surfaces.

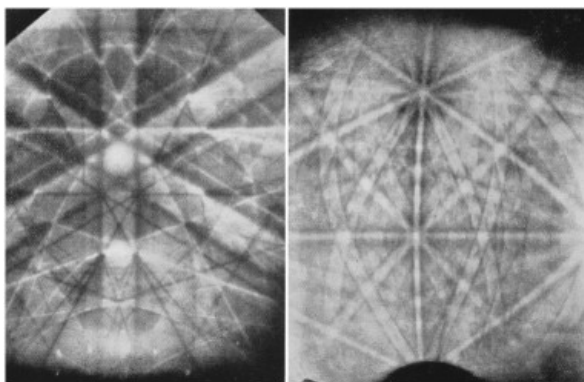

Backscatter Kikuchi patterns obtained from iron (left) and fluorspar (fluorite) (right), recorded on a cylindrical film at 20 kV.


Boersch used flat photographic plates as well as a cylindrical specimen chamber with a cylindrical film to record high-angle Kikuchi patterns. The angular range is considerably larger than that obtained before in the TEM and in present SEM appliances. The patterns are remarkably sharp and rich in detail. The widths of the bands was found, in agreement with Bragg's law, to be related to the energy of the incident beam and the interplanar lattice spacings.

Boersch has discussed the origin of Kikuchi lines, dark and bright bands and envelopes taking von Laue's dynamical theory of electron diffraction into consideration.

G.I. Finch and H. Wilman

The study of surface structures by electron diffraction.

Ergebnisse der exakten Naturwissenschaften **16** (1937) 353-436

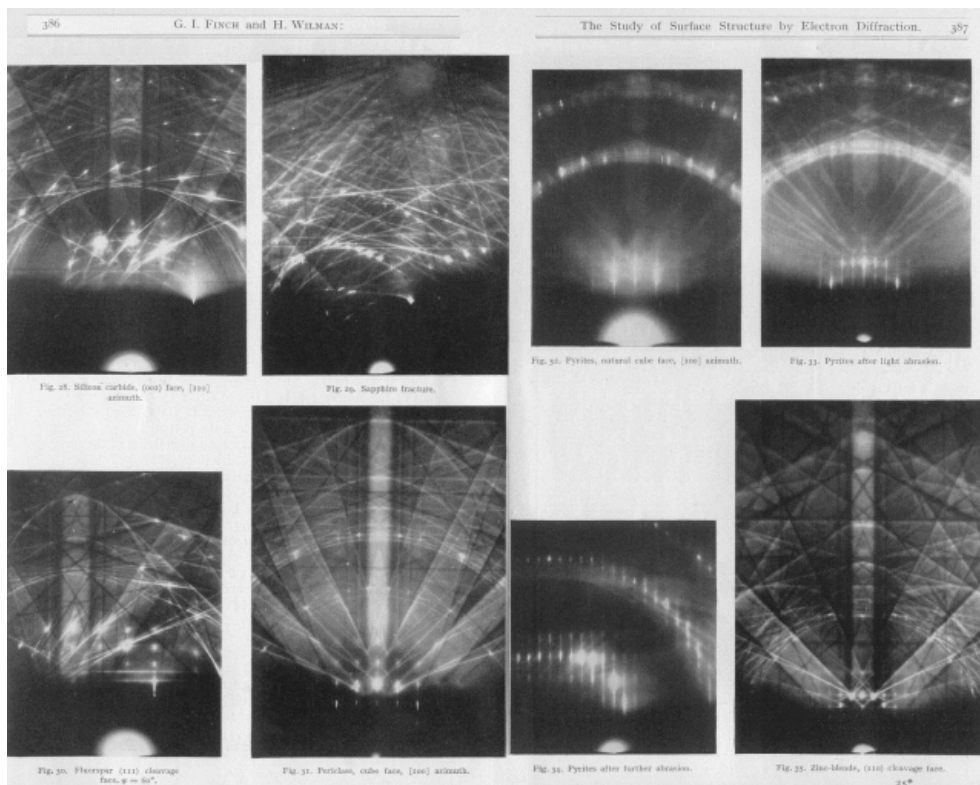

In this review a collection of excellent backscatter Kikuchi patterns from a variety of single crystal cleavage faces have been presented.

1944 Max von Laue

and **Materiewellen und ihre Interferenzen.**

1948 Akademische Verlagsgesellschaft Geest & Portig K. G., Leipzig 19 44; reprint 1948

The intensity pattern outside a crystal due to a point source of charged particles inside the crystal was quantitatively explained by von Laue when he solved the problem of bands in patterns as observed by S. Kikuchi. Many examples of observed patterns and the theoretical development can be found in his book "*Particle Waves and Their Interferences*" (in German). After electrons are inelastically scattered the original spherical wave is considered as a superposition of several Bloch waves inside the crystal, taking appropriate boundary conditions at the crystal surface and absorption by imaginary structure potentials into account to determine the intensity pattern outside.

1947, K. Artmann

1948 **On the theory of Kikuchi envelops.** (paper in German)

Zeitschrift für Physik **124** (1947) 80-104, 154-174; **125** (1948) 27-58, 298-335

The formation of Kikuchi envelops is treated without using the reciprocity law as well as in a rigorous wave-dynamical treatment based on the reciprocity law, a one dimensional and a three dimensional periodic crystal lattice. A good agreement of both features, surface lattice envelops and crystal lattice envelops, with experimental findings has been obtained.

(Remark: Kikuchi envelops can have a ring shape or a parabolic appearance. Perhaps due to the similarity with HOLZ rings of spots in transmission electron diffraction on thin foils, the ring shaped envelops are sometimes named "HOLZ lines" in recent publications even in the case of BKD. One should, however, bear in mind that Kikuchi envelops are definitively an effect of dynamical rather than kinematical diffraction. The Ewald construction is a very useful model for illustrating the formation of diffraction spots, but it is not applicable to BKD. In particular, there is no coherence between a primary beam and the diffracted beams.)

K. Artmann

On the theory of Kikuchi bands. (paper in German)

Zeitschrift für Physik **125** (1948) 225-249

The formation of Kikuchi patterns is treated by using the reciprocity law and solving the Schrödinger equation for bound electrons in the three dimensional crystal potential. This approach of dynamical theory of electron diffraction leads to a good agreement of the intensity profile and location of Kikuchi bands with experimental results.

Kossel patterns in X-ray diffraction closely correspond to Kikuchi patterns in electron diffraction. If they are generated with hard X-rays of, for instance, higher than 100 keV energy when X-ray wavelengths are in the range of the wavelengths of electrons in the SEM, the Kossel cones degenerate into almost straight lines so that these Kossel patterns look very similar to Kikuchi patterns.

["Download PDF"](#)  H. Determann

Kikuchi-Bänder mit Röntgenstrahlen. (in German with attached English translation)

Schriften der Naturforschenden Gesellschaft in Danzig 1938, pp. 5-7

H.C. Wolf:

Gitterquell-Interferenzen harter Röntgen-Bremsstrahlung. (in German).

Annalen der Physik **448** (1953) 381-403

Diffraction of ions, such as protons or He⁺, by single crystals can as well generate patterns very similar to Kikuchi patterns. They are known as Ion Blocking Patterns.


For details visit www.crystaltexture.com

..... many publications have appeared since then, for example:

- 1954 M.N. Alam, M. Blackman and D.W. Pashley
High-angle Kikuchi patterns.
 Proceedings of the Royal Society of London A **221** (1954) 224-242
 A cylindrical specimen chamber and camera have been used to study high-angle Kikuchi patterns obtained by reflection of electrons, of energy 6 to 50 keV, from the cleavage surfaces of crystals with the sodium chloride structure. Angles of scattering ranging from 0° to 164° were covered. The relative intensity of the patterns at different scattering angles was measured using a photographic technique. The intensity distribution was found to become less steep as the energy of the incident electrons decreased. In photographs taken with a large value of the glancing angle of incidence, defect bands were found, starting near the shadow edge of the pattern. These changed to excess bands at higher angles of scattering.
 The most striking feature of the results is the remarkable intensity and clarity at the highest scattering angles of the patterns produced by crystals such as lead sulphide and potassium iodide, the constituents of which have a relatively high elastic scattering cross-section. In marked contrast, a relatively low intensity and low clarity was found at these angles for lithium fluoride under the same experimental conditions. An investigation of the width of Kikuchi bands, visible over the whole available angular range, showed that the electrons forming these bands had the same energy as that of the incident electrons within the experimental error of 10%. A possible mechanism is discussed by means of which electrons can be diffused through large angles with high efficiency, relative to small angles, and with relatively little loss of energy.
 In essence, the findings of H. Boersch (1937, see above) have been confirmed.
- 1973 J.A. Venables, C.J. Harland
 Video camera attached to the SEM. They have coined the new term "*EBSP*" (= *Electron BackScatter Patterns*) for backscatter Kikuchi patterns.
- 1987 D. Dingley & Link: 1st commercial system for the SEM
The user had to identify and locate 3 zone axes on the screen, then the program calculated the rotation matrix; feasible for cubic crystal symmetry.
- 1990 N.-H. Schmidt (Risø; HKL): commercial system ("Channel")
The user had to mark interactively 3 or more bands to automatically index the pattern.
- 1992 N. Krieger Lassen, D. Juul Jensen, K. Conradsen
Automated indexing using the Hough transform and a butterfly mask
- 1993 B.L. Adams, S.I. Wright
"OIM": mechanical stage scan; Burns algorithm, Hough transform.
- 1994 Niels Krieger Lassen (PhD Thesis at Risø and Univ. Lingby, Denmark) *Thorough investigation of the Hough transform for automated EBSD.*

Some of our contributions

- 1989 (Peltier cooled) CCD camera employed for BKD
- 1993 Intensified CCD camera, interactive measurement of BKD band positions with the cursor on the monitor screen, automated indexing and orientation calculation.
Modified ORKID/TEM version, supports all crystal symmetries.
- 1994 Digital beam scan for automated BKD
- 1997 ACOM (ORKID/SEM)
The SEM is operated under full control of ACOM software:
 . dynamic focusing and dynamic system calibration,
 . automatic setup calibration,
 . all working distances and magnifications of the SEM are available for ACOM,
 . automatic acquisition of flat images,
 . Radon transform (RT) for automated extraction of band positions, *no butterfly mask is used*,
 . Pattern quality computed from RT and 1D FFT.
- 1998 Iterative refinement of the scanning grid ("*mesh refinement*")

- 2001 Pattern solving by the combination of *Radon Transform* with *Artificial Neural Networks* (ANN, artificial intelligence)
- 2007 Fast EBSD in cooperation with Prof. Dr. Jarle Hjelen, Trondheim
- 2009 EBSD detector employed as a multi-array detector to construct microstructure images which reveal topographic, material Z as well as lattice directional contrast during the acquisition of pattern sequences on-line or off-line in FastEBSD (see [Poster Kiel 2011](#) ).

Basics	TKD	Radon vs Hough	FastEBSD	Evaluation	Conclusions	Publications	Downloads	Glossary
--------	-----	----------------	----------	------------	-------------	--------------	-----------	----------